

---

Submitted: 2023-06-23 | Revised: 2023-09-15 | Accepted: 2023-09-21

*Keywords: friction welding, friction coefficient, finite element method, frictional heating*

Andrzej ŁUKASZEWICZ [0000-0003-0373-4803]\*, Jerzy JÓZWIK [0000-0002-8845-0764]\*\*,  
Kamil CYBUL [0009-0008-4321-3045]\*\*\*

## IMPACT OF FRICTION COEFFICIENT VARIATION ON TEMPERATURE FIELD IN ROTARY FRICTION WELDING OF METALS – FEM STUDY

### Abstract

*A mathematical model is presented for investigating the temperature field caused by the rotary friction welding of dissimilar metals. For this purpose, an axisymmetric, nonlinear, boundary value problem of heat conduction is formulated with allowance for the frictional heating of two cylindrical specimens of finite length made of Al 6061 aluminium alloy and 304 stainless steel. The thermo-physical properties of materials change with increasing temperature. It was assumed that the coefficient of friction does not depend on the temperature. The mechanism of heat generation due to friction on the contact surface with the temperature field of samples is considered. The boundary problem of heat conduction was reduced to the set of nonlinear ordinary differential equations at time  $t$  relative to the values of temperature  $T$  at the finite elements nodes. The numerical solution of the problem was obtained with the inverse 2nd order differentiation method implemented in COMSOL FEM system (finite element method), with time step  $\Delta t=0.1$  (s). The influence of various values of friction coefficient is presented.*

### 1. INTRODUCTION

Friction welding is a widely used solid-state joining process. Metallic and nonmetallic materials with different thermomechanical properties can be welded Simoes et al. (2014), Uday et al. (2012) and Taban et al. (2010). The friction welding processes can be divided into the following types: continuous drive friction welding (CDFW) or rotary friction welding (RFW), inertia friction welding (IFW), linear friction welding (LFW), orbital friction welding (OFW) and friction stir welding (FSW). The CDFW is the oldest and most used method. One of the most effective numerical method for structural and thermal

---

\* Białystok University of Technology, Faculty of Mechanical Engineering, Institute of Mechanical Engineering, Wiejska 45 c, 15-351 Białystok, Po-land, a.lukaszewicz@pb.edu.pl

\*\* Lublin University of Technology, Faculty of Mechanical Engineering, Department of Production Engineering, Nadbystrzycka 38 D, 20-618 Lublin, Poland, j.jozwik@pollub.pl

\*\*\* Lublin University of Technology, Doctoral School at the Lublin University of Technology, Nadbystrzycka 38 B/406, 20-618 Lublin, Poland, k.cybul@pollub.pl

problems is the finite element (FE) method. Several studies have so far been made to investigate the thermal problem of friction welding. A review papers on this question was presented for example in the works by Maalekian (2007), Uday et al. (2010), Gooch T. G. (1973) and Bhamji et al. (2011). In work of Pinheiro (2019) the welding of aluminum ASTM A6351-T6 and SAE 1020 steel was carried out aiming at evaluating the effects of the initial contact geometry on the mechanical properties of the welded joint in detail.

In work by Uday et al. (2012) axisymmetric FE model of the CDFW has been developed to analyse a temperature field of friction pair: Al 6061 aluminium alloy and 304 stainless steel. The same pair (Al 6061 + AISI 304) was experimentally tested by Senkathir and Siddharth (2020). Taban et al. (2010) analysed dissimilar friction welding of 6061–T6 aluminum and AISI 1018 steel, properties and microstructural characterization. Effect of energy input on tensile strength of 304-304 bars during CDFW was examined in the paper developed by Wang et al. (2018).

Influence of varying rotational speed on the tensile static strength and tension-compression fatigue behaviours for AA7075/AA5083 aluminium alloys pair carried out using RFW was performed by Sasmito et al. (2022). Linear and rotary friction welding in detail are analysed by Li et al. (2016). FSW process (Rajak et al. 2020) and study on grain boundary and microtexture evolutions during FSW of aluminum alloys (Shamanian et al. 2016) were analysed. Fatigue performance of Al2024 alloy performed by FSW process in a different corrosive environment were studied by Thapliyal and Dwivedi (2020), Ross and Sorensen (2013) as well as by Chen and Cui (2018). Optimization of parameters in RFW process of dissimilar austenitic and ferritic stainless steel using finite element analysis were analysis in Mattie et al. (2023). Many researchers deal with the friction welding of aluminum alloys in great detail, for example: Ghias et al. (2019), Mehta (2019). Livingston (2019) in their PhD thesis presented comparison of heat generation models using finite element analysis during friction welding process.

The aim of this paper is to show the influence of friction coefficient's values for temperature distribution in frictional heating stage in RFW process. The present work is a continuation of the research carried out by Łukaszewicz (2018, 2019). In these studies, the nonlinear numerical model using FEM for simulate temperature field near contact zone in the RFW process for metals alloys were developed, modelled and analysed.

## 2. MATERIALS AND METHODS

A friction stage of CDFW process is considered (Fig. 1). Assembly of two cylindrical parts by rotational friction when applying a compression, constant pressure  $p_0$  generates heat at the contact zone. One part is stationary while the second is rotating with constant value  $\omega_0$  in predetermined time  $t_s$ . After this stage the rotation is stopped and final forging pressure is applied to make the weld. It is assumed that the properties of materials are temperature dependent.

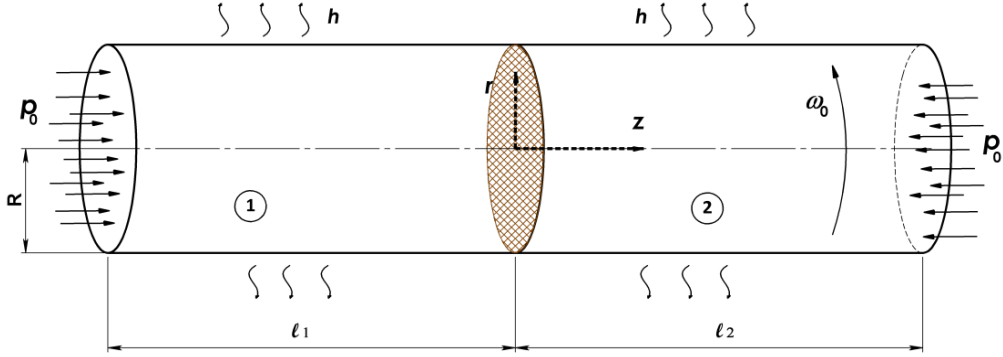


Fig. 1. Schematic diagram of frictional system in CDFW process

Axisymmetric transient temperature field  $T(r, z, t)$  will be obtained from the solution of the following boundary value problem of heat conduction in the cylindrical coordinate system (if  $l_1 = l_2 = l$ ) (Łukaszewicz, 2018):

$$\frac{1}{r} \frac{\partial}{\partial r} \left[ r K_1(T) \frac{\partial T}{\partial r} \right] + \frac{\partial}{\partial z} \left[ r K_1(T) \frac{\partial T}{\partial z} \right] = \rho_1(T) c_1(T) \frac{\partial T}{\partial t}, 0 < r < R, 0 < z < l, 0 < t \leq t_s, \quad (1)$$

$$\frac{1}{r} \frac{\partial}{\partial r} \left[ r K_2(T) \frac{\partial T}{\partial r} \right] + \frac{\partial}{\partial z} \left[ r K_2(T) \frac{\partial T}{\partial z} \right] = \rho_2(T) c_2(T) \frac{\partial T}{\partial t}, 0 < r < R, -l < z < 0, 0 < t \leq t_s, \quad (2)$$

$$K_2 \frac{\partial T}{\partial z} \Big|_{z=0^-} - K_1 \frac{\partial T}{\partial z} \Big|_{z=0^+} = q(r, t), 0 \leq r \leq R, 0 < t \leq t_s, \quad (3)$$

$$T(r, 0^-, t) = T(r, 0^+, t), 0 \leq r \leq R, 0 < t \leq t_s, \quad (4)$$

$$K_1(T) \frac{\partial T}{\partial r} \Big|_{r=R} = h[T(R, z, t) - T_0], 0 \leq z \leq l, 0 < t \leq t_s, \quad (5)$$

$$K_2(T) \frac{\partial T}{\partial r} \Big|_{r=R} = h[T(R, z, t) - T_0], -l \leq z \leq 0, 0 < t \leq t_s, \quad (6)$$

$$\frac{\partial T}{\partial z} \Big|_{z=\pm l} = 0, 0 \leq r \leq R, 0 < t \leq t_s, \quad (7)$$

$$T(r, z, 0) = T_0, 0 \leq r \leq R, -l \leq z \leq l, \quad (8)$$

Temperature dependencies of thermal conductivity  $K_i$ , specific heat  $c_i$  and density  $\rho_i$ ,  $i = 1, 2$ ; of specimen materials have the form:

$$K_i(T) = K_{0,i} K_i^*(T), c_i(T) = c_{0,i} c_i^*(T), \rho_i(T) = \rho_{0,i} \rho_i^*(T), \quad (9)$$

$$K_{0,i} = K_i(T_0), c_{0,i} = c_i(T_0), \rho_{0,i} = \rho_i(T_0). \quad (10)$$

where:  $K_i^*(T)$ ,  $c_i^*(T)$ ,  $\rho_i^*(T)$  are dimensionless functions of temperature.

In general case, owing to the high temperatures on the contact surface, the friction coefficient  $f$  should be dependent on the temperature:


$$f(T) = f_0 f^*(T), f_0 = f(T_0). \quad (11)$$

The specific friction power, taking into account equation (3), equals (Łukaszewicz, 2019):

$$q(r, t) = q_0 q^*(r, t), q_0 = f_0 p_0 R \omega_0, q^*(r, t) = r R^{-1} f^*[T(r, 0, t)], 0 \leq r \leq R, 0 \leq t \leq t_s. \quad (12)$$


### 3. RESULTS

Simulation of frictional heating in a couple during friction process with parameters:  $f(T) = f_0 = 0.1; 0.2; 0.4$ ,  $p_0 = 40$  (MPa),  $\omega_0 = 146.6$  (rad/s),  $h = 40$  (W/m<sup>2</sup>K),  $t_s = 1$  (s) using FE based software (COMSOL Multiphysics v.5.2a) was carried out. The calculations were performed for two specimens of radius  $R = 12.5$  (mm) and length  $l = 50$  (mm) each, made of Al 6061 aluminium alloy and 304 stainless steel. The 2D axisymmetric FE mesh of the friction couple is shown in Figure 2.

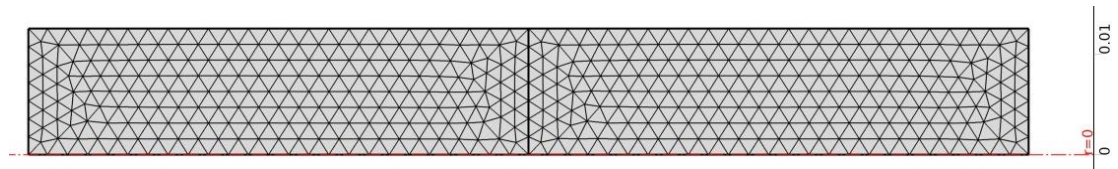


**Fig. 2. FE mesh of the friction pair**

Changing the properties of Al 6061 aluminium alloy with temperature increase is shown in Figure 3, and the properties of temperature dependence of 304 stainless steel is presented in Figure 4 (Rothman, 1988). On Figure 3 and 4 following units are applied:  $K_i(T)$  (W/(m K)),  $c_i(T)$  (J/(kgK)),  $\rho_i(T)$  (kg/m<sup>3</sup>); x axis:  $T$  (K).

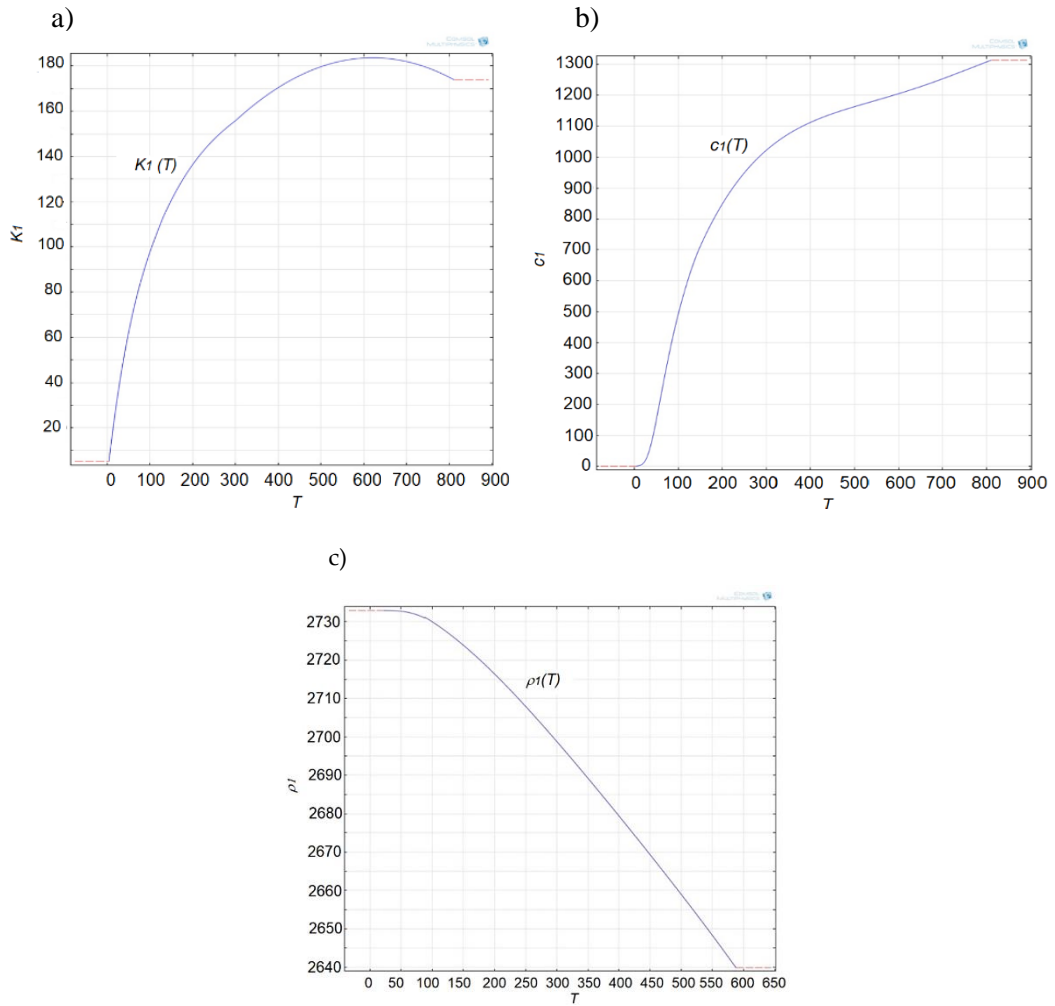


**Fig. 3. Functions  $K_1(T)$  (a),  $c_1(T)$  (b),  $\rho_1(T)$  (c) for Al 6061 aluminium alloy**

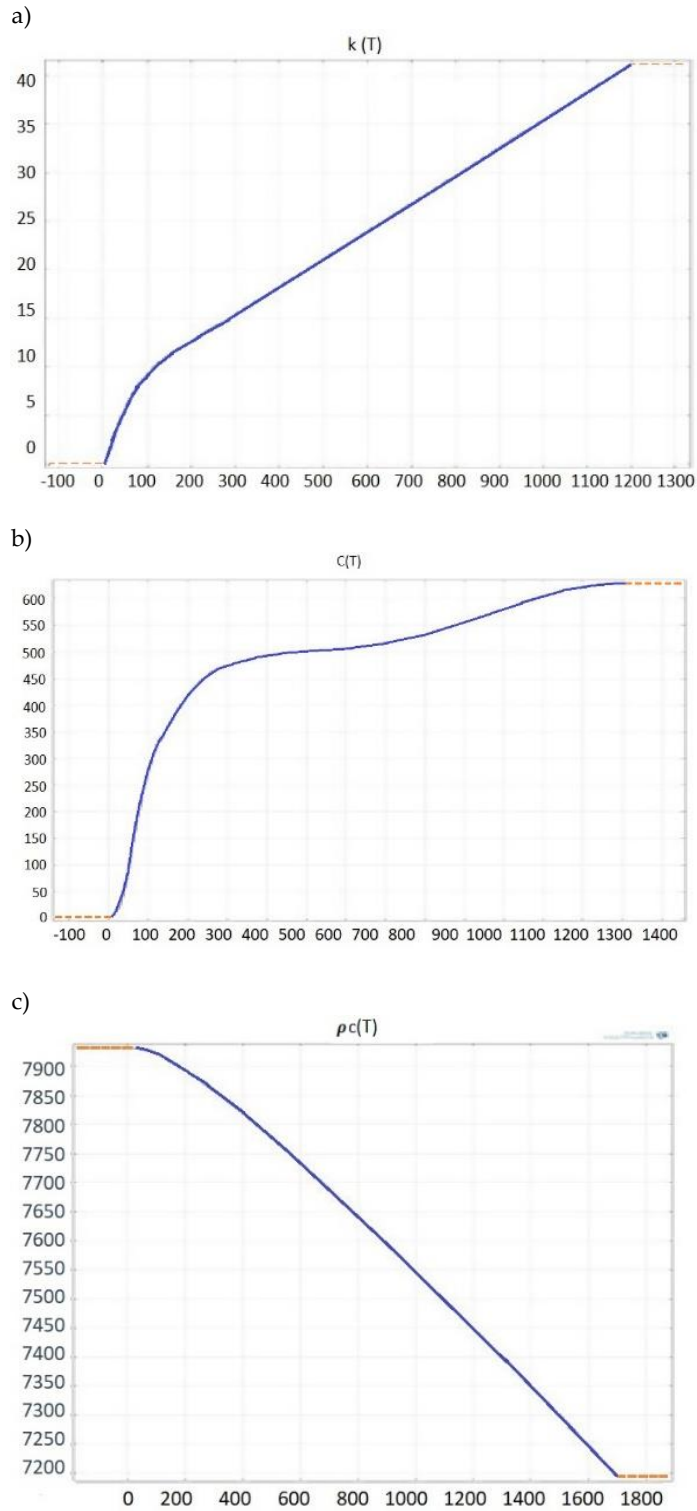

**Fig. 4. Functions  $K_2(T)$  (a),  $c_2(T)$  (b),  $\rho_2(T)$  (c) for 304 stainless steel**

The two-dimensional region was filled by triangular finite 2<sup>nd</sup> order element. Number of finite elements was 844. Influence of number of FE in similar axisymmetric problem to calculation results is described in paper by Łukaszewicz (2018). Difference between results of  $T_{max}$  (°C) on whole contact surface for two identical specimens made of AISI 1040 steel ( $l_1 = l_2 = 30$  (mm),  $R = 6$  (mm)) in case of numbers of FE equal respectively 460 and 6062 was less than 0.015 %. In presented paper, the impact of quantity of FE was not discussed. However, according to previous author calculation experiences, the relative error in the specified amount of FE (i.e. 844) certainly will not be greater than 0.1% if the amount of FE will increase to about 10 times (e.g. 10000).

As a result of described discretization, the boundary problem of heat conduction was reduced to the set of nonlinear ordinary differential equations on time  $t$  relative to the values of temperature  $T$  in the finite elements nodes. The solution was obtained with the inverse 2<sup>nd</sup> order differentiation method implemented in COMSOL FEM system, with time step  $\Delta t = 0.1$  (s).

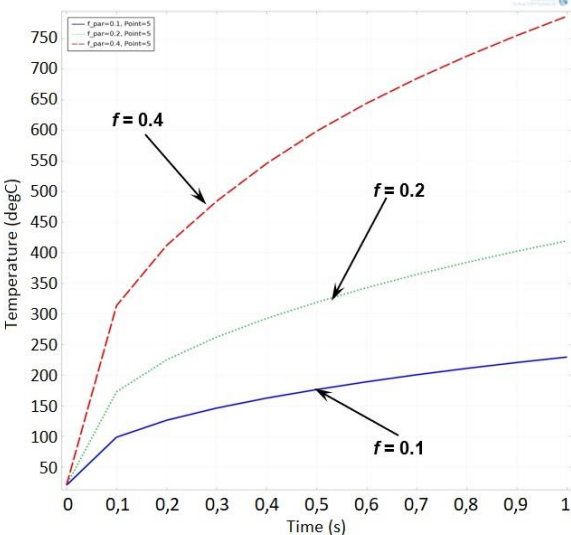

**Fig. 5. Evolution of temperature  $T$  (°C) with time  $t$  (s) on the contact surface  $z = 0, r = R$  for three values of friction coefficient  $f$**

The effect of various values of friction coefficient on temperature was considered. It was found that an increase in the parameter  $f$  leads to an increase in the temperature in contact surface ( $z = 0$ ) for  $r = R$  during the entire heating process (Fig. 5). The temperature increases the most at the outer surface ( $r = R$ ) for  $t = t_s$  (Fig. 6). This is due to the higher linear velocity  $v = \omega_0(r)$  as the radius  $r$  increases, and thus the higher value of the specific friction force  $q(r, t)$ .

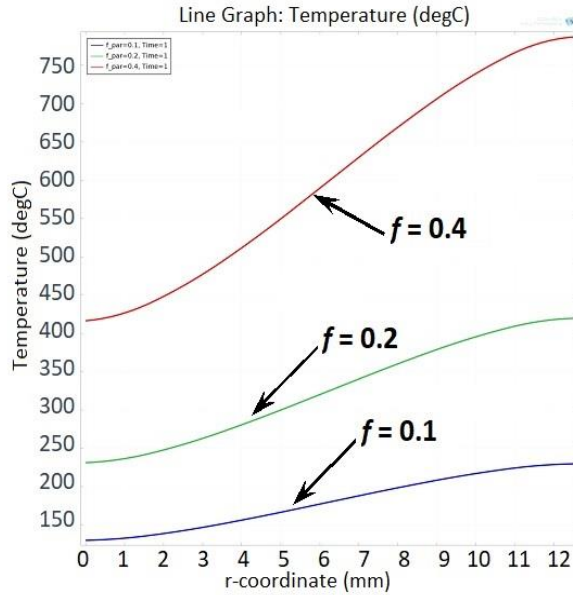


Fig. 6. Change of temperature  $T$  ( $^{\circ}\text{C}$ ) on the contact surface  $z = 0$  in the radial direction  $r$  (mm) at time  $t = t_s$

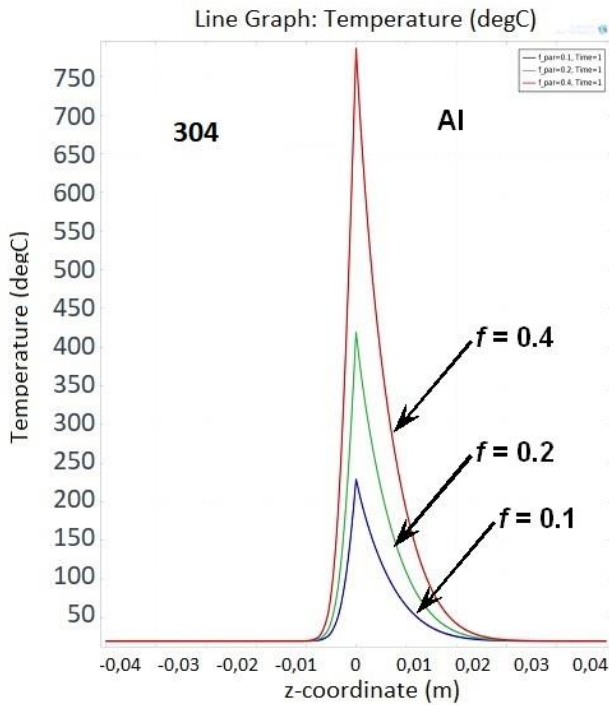


Fig. 7. Change of temperature  $T$  ( $^{\circ}\text{C}$ ) along  $z$  axis (m) at  $t = t_s$  for  $r = R$  for three values of friction coefficient  $f$



Figure 7 shows the effect of the value of the friction coefficient  $f$  on the temperature distribution in the axial direction  $z$  at the end of fictive heating ( $t = t_s$ ) for  $r = R$ . It was observed that an increase in the value of  $f$  leads to an increase in the temperature in contact surface ( $z = 0$ ) for  $r = R$  at the end of friction heating stage of welding process. Due to the higher thermal conductivity values for the aluminum alloy, the temperature influence zone on the Al 6061 side is wider than on the steel side.

Temperature obtained in contact zone for value of friction coefficient  $f = 0.4$  and at the time  $t = t_s$  (Fig. 6 and 7) is the most suitable to achieve a steel-aluminum friction pair joint, over the entire contact surface. However, the simulation would need to be verified experimentally to confirm whether this value of  $f$  allows for correct numerical results.

In fact, the value of the coefficient of friction during the friction welding process is not constant. However, obtaining the temperature characteristics of the friction coefficient for a given friction pair is not easy and requires specialized instrumentation. For this reason, many mathematical models often assume a constant value of this parameter for numerical simulations. In investigations carried out by Łukaszewicz (2018, 2019) it was assumed temperature-dependent characteristics of friction coefficient for similar friction steel pair AISI 1040/AISI 1040 find from work by Bouarroudj (2017). However, there is no database for the temperature characteristics of the friction coefficient  $f(T)$  for dissimilar friction pairs.

#### 4. CONCLUSIONS

A mathematical model is proposed for investigating the temperature field caused by the rotary friction welding of dissimilar metals. For this purpose, an axisymmetric, nonlinear, boundary value problem of heat conduction is formulated with allowance for the frictional heating of two cylindrical samples of finite length made of Al 6061 aluminum alloy and 304 stainless steel. It is assumed that the both materials of specimens are thermally sensitive, but the friction coefficient is independent of temperature. The numerical solution of the problem is obtained by the finite element method. The influence of various values of friction coefficient has been considered. For this friction pair value of friction coefficient  $f = 0.4$  is the most suitable to obtain the realistic temperature, allowing to achieve a steel-aluminum friction pair joint, over the entire contact surface. Presented results are important and significant not only in the scientific but also in the utilitarian sense. They allow optimizing the parameters of the friction welding process and affect the energy parameters of the process.

#### Author Contributions

*The authors confirms sole responsibility for the following: study conception and design, analysis and interpretation of results, and manuscript preparation.*

#### Funding

*This research was financed by the Ministry of Science and Higher Education of Poland with allocation to the Faculty of Mechanical Engineering Bialystok University of*

*Technology for the WZ/WMIIM/ 5/2023 academic project in the mechanical engineering discipline.*

## **Acknowledgments**

*The paper was made as part of the project No DWD/6/0116/2022, titled: “Improving the relative uncertainty of measurement by developing and implementing a new force reference standard up to 100 kN into the national metrological infrastructure”, framework Polish Ministry of Education and Science Program: Implementation PhD III - metrology*

## **Conflicts of Interest**

*The authors declare no conflict of interest.*

## **REFERENCES**

- Bhamji, I., Preuss, M., Threadgill, P. L., & Addison, A. C. (2011) Solid state joining of metals by linear friction welding: a literature review. *Materials Science and Technology*, 27(1), 2–12. <https://doi.org/10.1179/026708310X520510>
- Bouarroudj, E., Chikh, S., Abdi, S., & Miroud, D. (2017) Thermal analysis during a rotational friction welding. *Applied Thermal Engineering*, 110, 1543–1553. <https://doi.org/10.1016/j.applthermaleng.2016.09.067>
- Chen, Z. W., & Cui, S. (2008) On the forming mechanism of banded structures in aluminium alloy friction stir welds. *Scripta Materialia*, 58(5), 417–420. <https://doi.org/10.1016/j.scriptamat.2007.10.026>
- COMSOL Multiphysics v. 5.2a. [www.comsol.com](http://www.comsol.com). COMSOL AB, Stockholm, Sweden.
- Ghias, S. A., Vijaya, R. B., Elanchezian, C., Siddhartha, D., & Ramanan, N. (2019) Analysis of the friction welding mechanism of low carbon steel–stainless steel and aluminium–copper. *Materials Today: Proceedings*, 16(2), 766–775. <https://doi.org/10.1016/j.matpr.2019.05.157>
- Gooch, T. G. (1973) Friction welding. *International metallurgical reviews*, 18(1), 42–42. <https://doi.org/10.1179/imttr.1973.18.1.42>
- Li, W., Vairis, A., Preuss, M., & Ma, T. (2016) Linear and rotary friction welding review. *International Materials Reviews*, 61(2), 71–100. <https://doi.org/10.1080/09506608.2015.1109214>
- Livingston, R. V. (2019) *Comparison of heat generation models in finite element analysis of friction welding*. PhD Tesis. Brigham Young University.
- Łukaszewicz A. (2019) Temperature field in the contact zone in the course of rotary friction welding of metals. *Materials Science*, 55(1), 39–45. <https://doi.org/10.1007/s11003-019-00249-4>
- Łukaszewicz, A. (2018) Nonlinear numerical model of heat generation in the rotary friction welding. *Journal of Friction and Wear*, 39(6), 476–482. <https://doi.org/10.3103/S1068366618060089>
- Maalekian, M. (2007). Friction welding – critical assessment of literature. *Science and Technology of Welding and Joining*, 12(8), 738–759. <https://doi.org/10.1179/174329307X249333>
- Mattie, A. A., Ezdeen, S. Y., & Khidhir, G. I. (2023) Optimization of parameters in rotary friction welding process of dissimilar austenitic and ferritic stainless steel using finite element analysis. *Advances in Mechanical Engineering*, 15(7), <https://doi.org/10.1177/16878132231186015>
- Mehta, K. P. (2019) A review on friction-based joining of dissimilar aluminum–steel joints. *Journal of Materials Research*, 34, 78–96. <https://doi.org/10.1557/jmr.2018.332>
- Pinheiro, M.A., & Bracarense, A.Q. (2019). Influence of initial contact geometry on mechanical properties in friction welding of dissimilar materials aluminum 6351 T6 and SAE 1020 Steel. *Advances in Materials Science and Engineering*, 1759484. <https://doi.org/10.1155/2019/1759484>
- Rajak, D. K., Pagar, D. D., Menezes, P. L., & Eyvazian, A. (2020) Friction-based welding processes: friction welding and friction stir welding. *Journal of Adhesion Science and Technology*, 34(24), 2613–2637. <https://doi.org/10.1080/01694243.2020.1780716>

- Ross, K., & Sorensen, C. (2013). Advances in temperature control for FSP. In Mishra, R., Mahoney, M.W., Sato, Y., Hovanski, Y., Verma, R. (Eds.), *Friction Stir Welding and Processing VII* (pp. 301–310). Springer. [https://doi.org/10.1007/978-3-319-48108-1\\_31](https://doi.org/10.1007/978-3-319-48108-1_31)
- Rothman M.F. (1988) *High-Temperature Property Data: Ferrous Alloys*. ASM Int., Ohio.
- Sasmito, A., Ilman, M. N., Iswanto, P. T., & Muslih, R. (2022). Effect of rotational speed on static and fatigue properties of rotary friction welded dissimilar AA7075/AA5083 aluminium alloy joints. *Metals*, 12(1), 99. <https://doi.org/10.3390/met12010099>
- Senkathir S., Siddharth V.B. (2020). Friction welding of dissimilar metals (aluminium AL 6061 T6 and stainless steel AISI 304). *IOP Conference Series Materials Science and Engineering*, 912(3), 032043. <https://doi.org/10.1088/1757-899X/912/3/032043>
- Shamanian, M., Mostaan, H., Safari, M., & Szpunar, J. A. (2016) EBSD study on grain boundary and microtexture evolutions during friction stir processing of A413 cast aluminum alloy. *Journal of Materials Engineering and Performance*, 25(7), 2824–2835. <https://doi.org/10.1007/s11665-016-2141-1>
- Simoës, F., & Rodrigues, D. M. (2014). Material flow and thermo-mechanical conditions during Friction Stir Welding of polymers: Literature review, experimental results and empirical analysis. *Materials & Design*, 59, 344–351. <https://doi.org/10.1016/j.matdes.2013.12.038>
- Taban, E., Gould, J. E., & Lippold, J. C. (2010). Dissimilar friction welding of 6061–T6 aluminum and AISI 1018 steel: properties and microstructural characterization. *Materials & Design*, 31(5), 2305–2311. . <https://doi.org/10.1016/j.matdes.2009.12.010>
- Thapliyal, S., & Dwivedi, D. K. (2020) Fatigue performance of friction stir welded Al2024 alloy in a different corrosive environment. *Materialwissenschaft und Werkstofftechnik*, 51,(2), 174–180. <https://doi.org/10.1002/mawe.201800171>
- Uday, M. B., Ahmad Fauzi, M. N., Zuhailawati, H. & Ismail, A. B. (2010) Advances in friction welding process: a review, *Science and Technology of Welding and Joining*, 15(7), 534–558. <https://doi.org/10.1179/136217110X12785889550064>
- Uday, M. B., Ahmad-Fauzi, M.N., Zuhailawati, H., & Ismail, A.B. (2012). Thermal analysis of friction welding process in relation to the welding of YSZ–alumina composite and 6061 aluminum alloy. *Applied Surface Science*, 258(20), 8264–8272. <https://doi.org/10.1016/j.apsusc.2012.05.035>
- Wang, G., Li, J., Wang, W., Xiong, J., & Zhang, F. (2018). Study on the effect of energy-input on the joint mechanical properties of rotary friction-welding. *Metals*, 8(11), 908. <https://doi.org/10.3390/met8110908>